

Inter- and Intraspecific Differences in Physical and Mechanical Properties of Wood from *Sclerocarya birrea* and *Anogeissus leiocarpus*

Fath Alrhman Awad Ahmed YOUNIS^{a,d*} – Abdelazim Yassin ABDELGADIR^b – Zeinab A. Abd Elhameed AHMED^b – James Kudjo GOVINA^{c,d} – Róbert NÉMETH^d

^a Department of Wood Science and Technology, Faculty of Forest Sciences and Technology, University of Gezira, Wad Madani - AL Gezira State, Sudan

^b Department of Forest Products and Industries, Faculty of Forestry, University of Khartoum- Khartoum North - Shambat area, Sudan

^c CSIR–Forestry Research Institute of Ghana, Kumasi, Ghana

^d Institute of Wood Technology and Technical Sciences, Faculty of Wood Engineering and Creative Industries, University of Sopron, Sopron, Hungary

Abstract – This paper studied the basic density and mechanical properties differences of wood among and within *Sclerocarya birrea* and *Anogeissus leiocarpus*. Three trees from each species were selected from the Lagawa Natural Forest Reserve in Western Kordofan State, Sudan. Test specimens were selected from three vertical positions (10, 50, and 90% along the bole length) of the trees. Specimens were also collected from three horizontal positions (innerwood, middlewood, and outerwood) within each of the three vertical positions. Tests for basic density of wood (BD), modulus of rupture (MOR), modulus of elasticity (MOE), compressive (CS), and shear strength (SS) parallel to the grain were performed. An analysis of variance shows that only the horizontal positions were a significant source of variation for both species studied. The correlation coefficient of BD was significant, weak, and positive for the mechanical properties of *A. leiocarpus*. A similar observation was found for BD correlated with CS and SS for *S. birrea*.

***Sclerocarya birrea* / *Anogeissus leiocarpus* / basic density / strength / modulus of elasticity**

Kivonat – A *Sclerocarya birrea* és az *Anogeissus leiocarpus* fajok közötti és fajokon belül kimutatható eltérések a faanyag fizikai és mechanikai tulajdonságaiban vonatkozásában. A kutatásban vizsgáltuk a *Sclerocarya birrea* és az *Anogeissus leiocarpus* faanyagok bázis sűrűségének és mechanikai tulajdonságainak változásait a két faj között és a fajokon belül. Minden fajhoz három faegyedet választottunk ki a szudáni Nyugat-Kordofan állambeli Lagawa Természeti Erdőrezervátumból. A próbatesteket három függőleges helyzetből (10, 50 és 90%-ban a törzshossz mentén) választottuk ki a fákon belül. Ezenkívül a mintákat három vízszintes helyzetből (belső farész, középső farész és külső faszövet) gyűjtöttük a három függőleges pozíció mindegyikén belül. Meghatároztuk a faanyag bázis sűrűségét (BD), vizsgáltuk továbbá a rostiránnyal párhuzamos hajlító szilárdságot (MOR), rugalmassági modulust (MOE), nyomószilárdságot (CS) és nyírószilárdságot. A varianciaanalízis azt mutatja, hogy mindkét vizsgált faj esetében csak a vízszintes helyzet mutatott jelentős eltérést. Az *A. leiocarpus* mechanikai tulajdonságai statisztikailag szignifikáns, de gyenge

* Corresponding author: BT8QC4@uni-sopron.hu; H-9400 SOPRON, Bajcsy-Zs. u. 4., Hungary

korrelációt mutattak a bázis sűrűséggel. A sűrűség növekedésével a szilárdságok is nőttek. A *S. birrea* fafajnál hasonló megfigyelést mutattunk ki, a sűrűség növekedésével nőtt a nyomó- és a nyírószilárdság.

***Sclerocarya birrea* / *Anogeissus leiocarpus* / bázis sűrűség / szilárdságok / rugalmassági modulusz**

1 INTRODUCTION

Wood is a natural material with many utilization purposes (Desch – Dinwoodie 1996). The distinctive features of wood (anisotropic, hygroscopic, orthotropic, and renewable) make it an easily recognizable material (Koch 1985). Generally, cellulose, hemicelluloses, and lignin ratios differ in wood components (Panshin – de Zeeuw 1980) between species. Moreover, these components vary between hardwood and softwood trees (Shmulsky – Jones 2011).

Several factors – including genetics, environment, site, age, and defects – contribute to wood variability (Desch – Dinwoodie 1996). These factors lead to the variation in the anatomical, physical, and mechanical properties of wood (Shmulsky – Jones 2011), which frequently weakens the acceptance of wood as a structural material (Desch – Dinwoodie 1996).

Variations in the physical and mechanical properties of wood among and within tree species have been extensively studied (Karki 2001, Steffenrem et al. 2007, Knapic et al. 2008, Chowdhury et al. 2009, Al-Sagheer – Prasad 2010, Chowdhury et al. 2013, Majumdar et al. 2014, Kiaei et al. 2015, Kiaei – Farsi 2016, Wessels et al. 2016, Xie et al. 2017 and Bektaş 2020). A previous study in Sudan revealed no significant source of variations in basic density within the wood of *Balanites aegyptiaca* (Awad 2015). However, significant sources of variations in wood density were found within *Tectona grandis* wood (Izekor et al. 2010). Wood variability attributed to variations between sites has been studied among *Pinus sylvestris* and *Acacia melanoxylon* in Portugal (Fernandes et al. 2017, Machado et al. 2014).

Sclerocarya birrea belongs to the Anacardiaceae family and can grow up to 12 m high (Vogt 1995). The wood is traditionally used for carving, furniture, saddles, and locally for manufacturing. Presently, the species is still important for sustaining rural livelihoods (Sahni 1968). In Sudan, *Sclerocarya birrea* can be found in places such as Kassala, Imatong Mountains, Erkwit, Blue Nile, Kordofan, and Darfur. The wood of *Sclerocarya birrea* is soft, diffuse-porous, and low to medium in density. The color of freshly cut wood is grayish with reddish bands and streaks, brown patches, and delivered to darkening reddish brown. The sapwood has been described as very wide, and it is not sharply differentiated from the heartwood (Goldsmith – Carter 1981).

Anogeissus leiocarpus (African birch) belongs to the Combretaceae family and can grow to a height of up to 20 m. Its wood has been locally used for transmission and building poles, fence posts, and forked poles. It is also used for beams in rural building construction. With its high energy characteristics, it is also used as firewood and for charcoal production. In Sudan, *Anogeissus leiocarpus* is found along streams and rivers and in valleys in South Kassala, Kordofan, South Darfur, and the Blue Nile states (El Amin 1990). The wood of *A. leiocarpus* is grayish outside, dark brown at the heart and very hard. The wood is ring porous and contains surface crystals and traumatic ducts (Ayeola et al. 2009).

Adequate scientific information on the technical properties of these two Sudanese species could lead to effective promotion and efficient utilization of their wood. The objective of this research was to investigate the variability of wood along the height of a tree and horizontal positions (innerwood, middlewood, and outerwood). The specific traits considered are basic density (BD), modulus of rupture (MOR), modulus of elasticity (MOE), compressive strength parallel to the grain (CS), and shear strength parallel to the grain (SS) within and among *S. birrea* and *A. leiocarpus* trees.

2 MATERIALS AND METHODS

2.1 Materials

Three trees each for species of *Sclerocarya birrea* and *Anogeissus leiocarpus* were randomly selected for the study. The trees were growing naturally in Lagawa Natural Forest Reserve located in the Western Kordofan State, Sudan, between 11°24'20"N - 29°8'18"E (Fig. 1). The trees were straight and free from natural defects. *Table 1* provides the basic morphological description of the sampled trees.

Table 1. Diameter at breast height (dbh), tree height and bole length for *Sclerocarya birrea* and *Anogeissus leiocarpus*

Species	Tree No.	Dbh (cm)	Tree height (m)	Bole length (m)
<i>S. birrea</i>	1	40	13	2.0
	2	42	16	2.5
	3	47	17	3.5
<i>A. Leiocarpus</i>	1	35	16	2.0
	2	38	15	2.6
	3	36	15.5	2.4

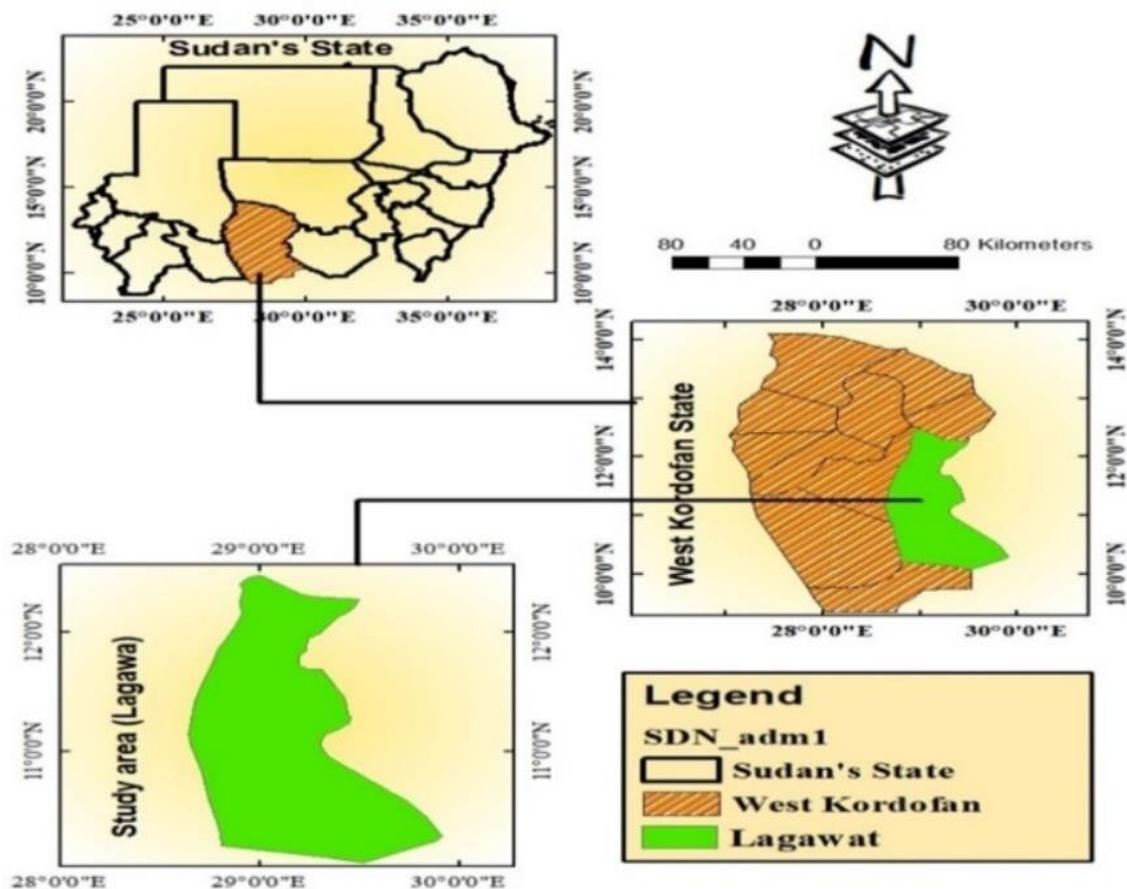


Figure 1. The study area

2.2 Methods

2.2.1 Sample collection and preparation

The trees were felled with a chainsaw and three 50-cm long sample logs were removed at 10, 50, and 90% along the bole length. The logs were sawn to 4 cm thick boards through the pith to the bark. Test specimens for the physical and mechanical properties were selected from wood around the pith, heartwood, and sapwood to represent innerwood, middlewood, and outerwood for each sampled log. Three replicates of test specimens were selected from each group (innerwood, middlewood, and outerwood). Other 20x20x30 mm specimens were taken from either end of all specimens prepared and used for mechanical testing to determine wood basic density based on oven-dry weight (W_o) per unit green volume (V_g) (ISO 3131 1975). The basic density of wood (BD g/cm^3) was calculated using the formula:

$$BD = W_o/V_g \quad (1)$$

The mechanical properties specimens were air-dried indoors to constant weight. The size of test specimens was 20x20x300 mm for MOR and MOE (ISO 3349 1975), 20x20x60 mm for CS (ISO 3787 1975), and 20x20x20 mm for SS (ISO 3347 1975). A universal testing machine was used to determine the mechanical properties. The following formulas were used to calculate the MOR, MOE, CS and SS (N/mm^2):

$$MOR = \frac{3 pl}{2 bd^2} \quad (2)$$

Where:

p:	load
l:	Length of span
b:	width
d:	depth.

$$MOE = \frac{pl^3}{4\Delta bd^3} \quad (3)$$

Where:

p:	load, at the limit of proportionality
l:	length of span
Δ :	deflection, at the limit of proportionality
b:	width
d:	depth.

$$CS = P/A \quad (4)$$

$$SS = P/A \quad (5)$$

Where:

P:	Maximum load
A:	Cross-sectional area.

2.3 Statistical Analysis

The data was organized in Microsoft Excel sheets and analyzed using SAS statistical package (SAS 1990). Nested analysis of variance was conducted using PROC Nested to investigate the significance of the variation among sources and their variance components (not to estimate the

means of the sources and the differences among them). Using PRPC CORR, the coefficients of correlation and regression were conducted to determine the relationship between mechanical properties and basic density. The significant correlation coefficients were classified as strong ($r \geq 70$), moderate ($r \geq 50 < 69$), and weak ($r \leq 49$). The tests were performed at the significant level of $P \leq 0.05$.

3 RESULTS AND DISCUSSION

3.1 Wood Basic Density (BD)

Table 2 presents the mean values of the basic density (BD) for the *S. birrea* and *A. leiocarpus* wood. The BD for all specimens ($n=1620$) of *S. birrea* varied from 0.35 to 0.79 g/cm^3 , and the mean value was 0.52 g/cm^3 . Basic density for *A. leiocarpus* ($n=1620$) varied from 0.68 to 1.28 g/cm^3 and the mean was 0.92 g/cm^3 . This study's mean BD for *S. birrea* is higher when compared to some reported values (0.49 g/cm^3) in Sudan (Mahgoub 2001). On the contrary, the study value was lower than the value (0.64 g/cm^3) reported in Saudi Arabia (Nasroun 2005). Similarly, *A. leiocarpus* wood has the greater BD in comparison to the values 0.82 g/cm^3 found by Mahgoub (2001), 0.88 g/cm^3 found by Mohammed (1999), and 0.731 g/cm^3 found by Ogunwusi et al. (2013). However, the study value was lower than the values of 1.150 g/cm^3 found by Bello-Jimoh (2018). The basic density of wood is the oven dry weight of wood material per green unit volume. Hence, it directly reflects the dry weight of wood as contained in freshly felled wood (Barnett – Jeronimidis 2003). At the same MC, one cubic meter of *A. leiocarpus* green wood is heavier than an equal volume of *S. birrea*. Based on the average BD, the oven-dry weight of one cubic meter of *S. birrea* green wood is estimated to be 520 kg and 940 kg for one cubic meter of *A. leiocarpus* wood. In some cases, it is of interest to estimate the weight of wood at a given MC if its dry weight is known. Then in both cases, the weight of one cubic meter will be multiplied by the actual wood volume to be transported. Figure 2 and Figure 3 show the mean basic density at the examined vertical (10, 50, and 90%) and horizontal positions (innerwood, middlewood and outerwood).

Table 2. Mean value and descriptive statistic for basic density of wood (g/cm^3) of *S. birrea* and *A. leiocarpus* trees. (Min): Minimum; (Max): Maximum; (Std dev): Standard deviation; (CV): Coefficient of variation

Species	Min	Mean	Max	Std dev	CV%
<i>S. birrea</i>	0.35	0.52	0.79	0.06	11.53
<i>A. leiocarpus</i>	0.68	0.92	1.28	0.08	8.69

Results of the variance analysis of the nested random effects (Table 3) show that trees and vertical positions within trees were not significant sources of variation in basic density for *S. birrea* ($p=0.96$ and $p=0.62$, respectively). Nevertheless, horizontal positions within vertical positions were a significant ($p=0.0001$) source of variation, although they contributed only 7.22% of the total variation. The percentage of the error variance component (92.77%) reveals that most of the variation in basic density was unexplained by the studied factors. Similar results were found for the basic density of *A. leiocarpus* in this study (Table 3). Trees and vertical position did not significantly influence basic density ($p=0.2$ and $p=0.07$, respectively). Rather, horizontal position was a significant source of variation ($p=0.0001$), contributing 25.74% of the total variation. The unexplained variation amounted to 54.93%. The observed variation in wood density among the horizontal positions (from innerwood to outerwood) for both species may be due to the increasing age of cambium (Chowdhury et al. 2009, Izekor et al. 2010).

These results agree with previous research findings that a horizontal position was a significant source of variation in the basic density for hardwood species such as *A. leiocarpus*, *Eucalyptus grandis* and *Eucalyptus camaldulensis* (Sadiku 2018, Wessels et al. 2016). Similarly, results agree with reports for softwood species such as *Juniperus polycarpus* (Kiaei et al. 2015) and *Pinus kesiya* (Missanjo – Matsumura 2016). However, the results are not in line with previous research findings that vertical positions within trees were a significant source of variation in hardwoods; for instance, within *Acacia nilotica* (Ahmed 1998); *Tectona grandis* (Izkor et al. 2010); *Corylus colurna* (Zeidler 2012); *Acacia saligna*, (Mmolotsi et al. 2013); *Balanites aegyptica* (Awad 2015), and *Albizzia julibrissin* (Kiaei - Farsi 2016).

Table 3. Nested random effects analysis of variance for basic density of *S. birrea* and *A. leiocarpus* wood. (**): $P < 0.0001$; (*): $P < 0.001$; (*): $P < 0.05$; (ns): not significant; (TR): tree; (VP): vertical position; (HP): horizontal position; (V comp): variable component

Variation sources	BD of <i>S. birrea</i>	BD of <i>A. leiocarpus</i>
TR	ns	ns
V comp%	0.00	0.00
VP(TR)	ns	ns
V comp%	0.00	0.00
HP(VP)	***	***
V comp%	7.22	25.74

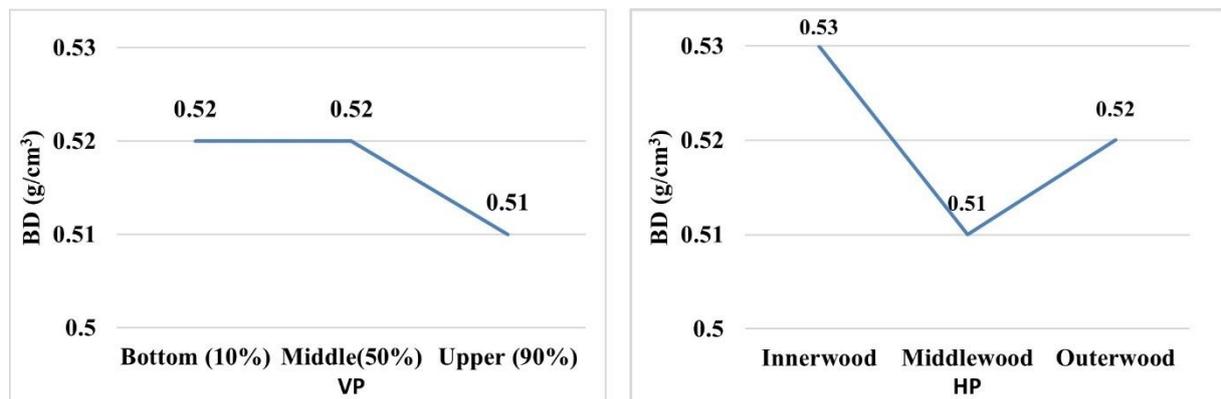


Figure 2. Showing the basic density within vertical and horizontal positions for *S. birrea*. (BD): basic density; (VP): vertical positions; (HP): horizontal positions

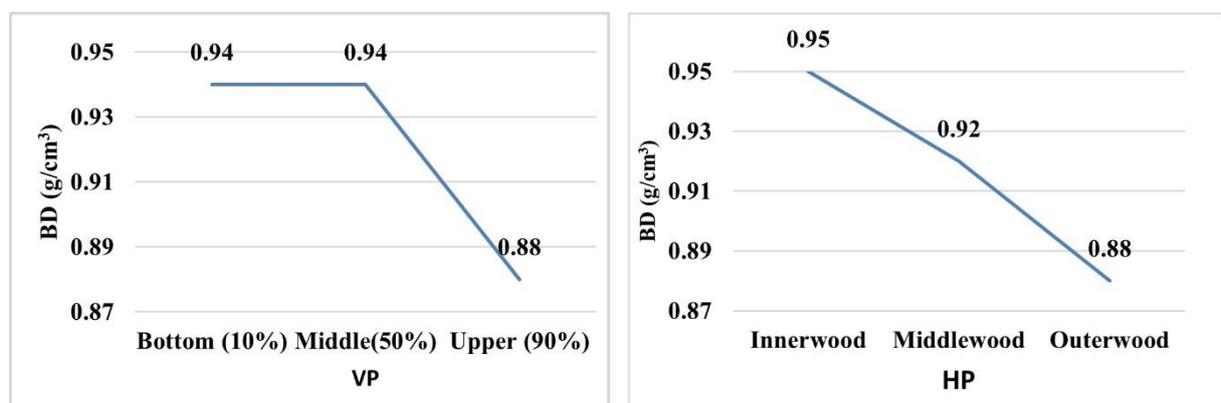


Figure 3. Showing the basic density within vertical and horizontal positions for *A. leiocarpus*. (BD): basic density; (VP): vertical positions; (HP): horizontal positions

3.2 Mechanical properties

Tables 4 and 5 present the mean values with standard deviation for the mechanical properties of *S. birrea* and *A. leiocarpus* wood. An analysis of variance of the nested random effects for mechanical properties shows that vertical positions (VP) were not a significant source of variation in the traits, except for MOR and MOE of *S. birrea* (Table 6). The same can be said for MOE and CS of *A. leiocarpus* (Table 7). However, the horizontal positions (HP) were a significant source of variation for both species in all traits. There are similar trends in mechanical properties among VP within trees of *Blانيتes aegyptiaca* (Awad 2015) and *Acacia melanoxylon* (Machado et al. 2014). The variations in mechanical properties among HP are probably due to several factors such as the density variability of the timber, cell arrangement and grain angle, and the microfibril angle within the cell wall (Panshin – de Zeeuw 1980). Figures 4 and 5 show the mean mechanical properties at the examined VP (10, 50, and 90%) and HP (innerwood, middlewood, and outerwood).

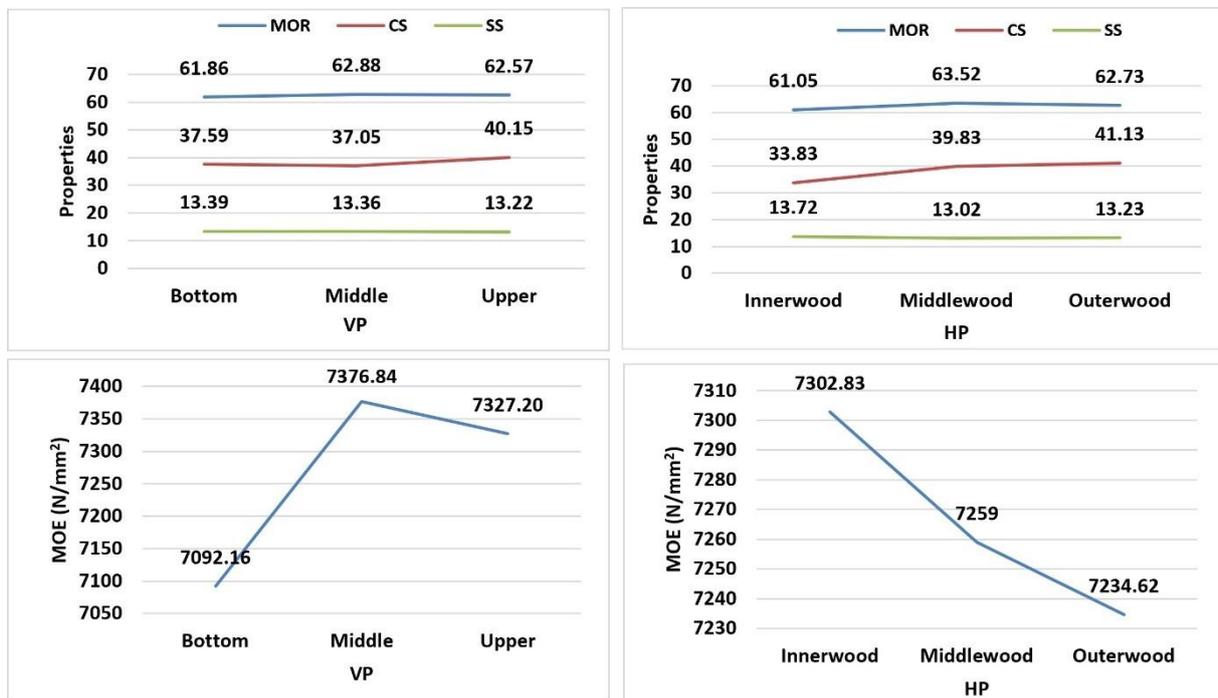


Figure 4. Showing the mechanical properties (N/mm²) within VP and HP for *S. birrea*. (VP): vertical positions; (HP): horizontal positions; (MOR): modulus of rupture; (MOE): modulus of elasticity; (CS): compressive strength parallel to the grain; (SS): shear strength parallel to the grain



Figure 5. Showing the mechanical properties (N/mm^2) within VP and HP for *A. leiocarpus*. (VP): vertical positions; (HP): horizontal positions; (MOR): modulus of rupture; (MOE): modulus of elasticity; (CS): compressive strength parallel to the grain; (SS): shear strength parallel to the grain

Table 4. Mean values and simple statistics of mechanical properties in (Nmm^2) of *S. birrea*. (MOR): modulus of rupture; (MOE): modulus of elasticity; (CS): compressive strength parallel to the grain; (SS): shear strength parallel to the grain

Variable	Min	Mean	Max	Std. dev	CV%
MOR	37.13	62.43	96.03	10	16.02
MOE	2884.41	7265.4	10935.7	1381.87	19.02
CS	12.37	38.26	51.39	6.87	17.96
SS	4.86	13.32	19.26	3.09	23.20

Table 5. Mean values and simple statistic of mechanical properties in (Nmm^2) of *A. leiocarpus*. (MOR): modulus of rupture; (MOE): modulus of elasticity; (CS): compressive strength parallel to the grain; (SS): shear strength parallel to the grain.

Variable	Min	Mean	Max	Std. dev	CV %
MOR	41.12	96.97	146.01	18.45	19.03
MOE	4958	12577	23553	3434	27.30
CS	30.55	45.77	68.45	6.85	14.96
SS	5.60	16.64	27.94	4.10	24.09

Table 6. Nested Random Effects Analysis of Variance for basic density and mechanical properties of *S. birrea* wood. (***): $P < 0.0001$; (**): $P < 0.001$; (*): $P < 0.05$; (ns): not significant; (TR): tree; (VP): vertical position; (HP): horizontal position; (V comp): variable component.

Variation sources	MOR	MOE	CS	SS
TR	***	***	ns	ns
V comp%	11.08	16.15	0.00	0.00
VP(TR)	ns	ns	ns	ns
V comp%	0.00	0.00	0.00	0.00
HP(VP)	***	**	***	***
V comp%	12.79	13.09	48.30	21.76

Table 7. Nested Random Effects Analysis of Variance for basic density and mechanical properties of *A. leiocarpus* wood. (***): $P < 0.0001$; (**): $P < 0.001$; (*): $P < 0.05$; (ns): not significant; (TR): tree; (VP): vertical position; (HP): horizontal position; (V comp): variable component.

Variation sources	MOR	MOE	CS	SS
TR	***	Ns	ns	*
V comp%	20.07	0.00	0.00	15.01
VP(TR)	ns	***	ns	ns
V comp%	0.00	17.44	0.00	0.00
HP(VP)	*	***	***	***
V comp	6.03	8.79	18.57	13.53

3.3 Relationships between mechanical properties and basic density

The results of Pearson correlation analysis of *S. birrea* reveal no significant correlation ($p=0.11$; $r=0.09$ and $p=0.37$; $r=0.05$) for MOR and MOE with BD. There was a significant but weak positive correlation for CS ($p=0.0004$; $r=0.21$) and SS ($p=0.0001$; $r=0.26$). There are contrary results for the correlation of MOR and MOE with BD among other wood species; for example, the wood of *Acacia nilotica* (DafaAlla 1998) and *Balanites aegyptiaca* (Awad 2015) in Sudan. Meanwhile, there were significant, weak positive correlations between all mechanical properties and BD of *A. leiocarpus* (Table 8).

The results of the correlation of mechanical properties with BD for both species studied were low, which suggests that relying on only the densities of the species for utilization can be a disadvantage. This suggestion agrees with Machado et al. 2014. The trends found by this study were not in agreement with the general perception that wood density had been considered a good indicator of wood strength (Shmulsky – Jones 2011). Previous research found significant, positive correlation of mechanical properties with wood density in *Tectona grandis* (Izekor et al. 2010) and *Borassus aethiopicum* (Asafu et al. 2013). However, their coefficients of correlation ranged between 0.85 to 0.90 %.

Regression coefficients for the significant and insignificant correlation were considered. The regression coefficients of determination (R^2) values ranged from 0.02 to 0.25, indicating that a small proportion of the variations in mechanical properties were explained by basic density. Consequently, coefficients of determination were low and did not indicate a good fit for both species Fig 6 and 7. Based on the results, the basic density of wood *S. birrea* and *A. leiocarpus* is not optimal to estimate the mechanical properties of the wood.

Table 8. Correlation coefficients (and probabilities) for mechanical properties with BD and of *S. birrea* and *A. leiocarpus*. (BD): basic density; (MOR): modulus of rupture; (MOE): modulus of elasticity; (CS): compressive strength parallel to the grain; (SS): shear strength parallel to the grain

Mechanical properties	BD of wood <i>S. birrea</i>	BD of wood <i>A. leiocarpus</i>
MOR	0.09 (0.11)	0.33 (0.0001)
MOE	0.05 (0.37)	0.28 (0.0001)
CS	0.21 (0.0004)	0.30 (0.0001)
SS	0.26 (0.0001)	0.24 (0.0001)

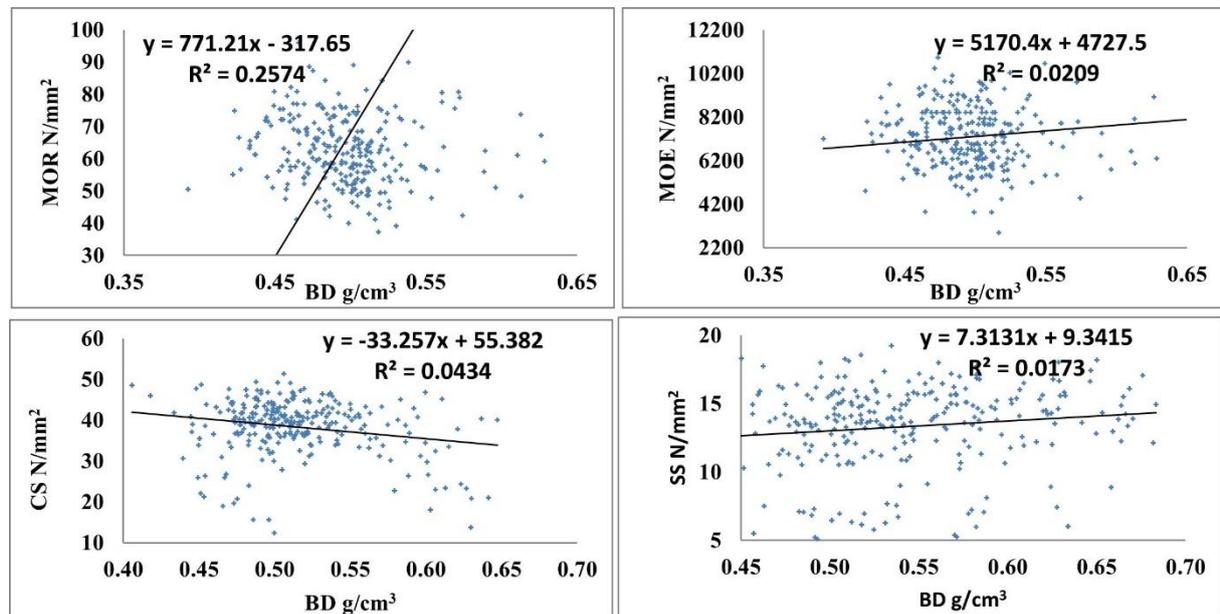


Figure 6. Relationships between mechanical properties and basic density of wood *S. birrea* tree. (BD): basic density; (MOR): modulus of rupture; (MOE): modulus of elasticity; (CS): compressive strength parallel to the grain; (SS): shear strength parallel to the grain.

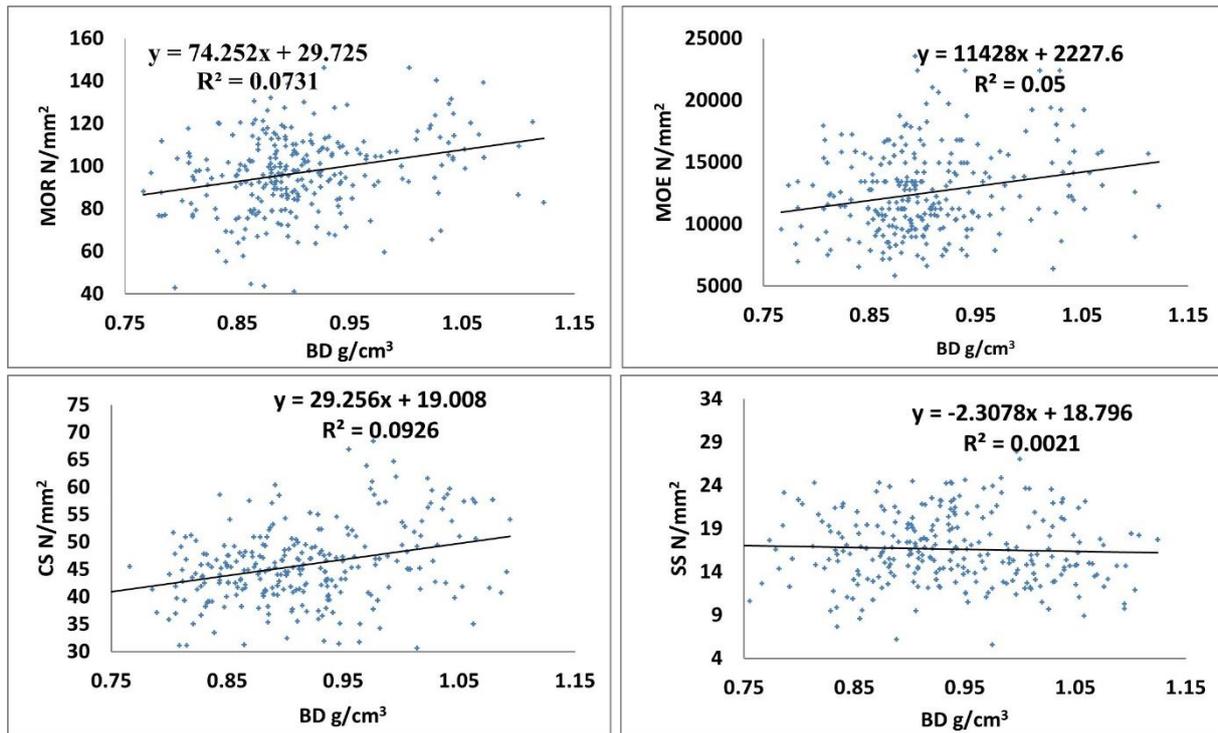


Figure 7. Relationships between mechanical properties and basic density of wood *A. leiocarpus* tree. (BD): basic density; (MOR): modulus of rupture; (MOE): modulus of elasticity; (CS): compressive strength parallel to the grain; (SS): shear strength parallel to the grain.

5 CONCLUSIONS

The present study draws the following conclusions:

- Horizontal position within vertical position was a significant source of variation in basic density and selected mechanical properties for *S. birrea* and *A. leiocarpus*.
- Vertical position within trees was not a significant source of variation in basic density for *S. birrea* and *A. leiocarpus*.
- Vertical positions within trees were a significant source of variation in MOR and MOE for *S. birrea*, and in MOE and CS for *A. leiocarpus*.
- The correlations of BD with the selected mechanical properties are significant, weak for *A. leiocarpus* and only with CS and SS for *S. birrea*.

Acknowledgements: We wish to thank the Ministry of Higher Education and Scientific Research in Sudan for partially funding this study. Thanks to Mr. Emad H. E. Yasin for preparing the map of the study area. Many thanks to Professor Bejő László for his comments to strengthen the article.

REFERENCES

- AL-SAGHEER, N. A. – PRASAD, A. G. D. (2010): Variation in Wood Specific Gravity, Density and Moisture Content of *Dipterocarpus indicus* (Bedd). among Different Populations in Western Ghats of Karnataka, India. *International Journal of Applied Agricultural Research* 5 (5): 583–599.
- ASAFU, A. O. A. – KWASI, F. M. – ALBERT, D. N. (2013): Assessment of the effects of density on the mechanical properties variations of *Borassus aethiopicum*. *Archives of Applied Science Research* 5 (6): 6–19.

- AWAD, M. E. (2015): Variation among trees, sites, and log position along the stem on physical and mechanical properties of Heglig wood (*Balanites Aegyptica*) growing in center Sudan. Master of Science Thesis, University of Khartoum.
- BARNETT, J. R. – JERONIMIDIS, G. (2003): Wood quality and its biological basis. Black Well Publishing. Ltd. Garsington.
- BEKTAŞ, I. – TUTUŞ, A. – GÜLTEKİN, G. (2020): The Effect of Sapwood and Heartwood Differences on Mechanical Properties of Fast-Growing Tree Species. *Drvna Industrija* 71 (3): 261–269. <https://doi.org/10.5552/drvind.2020.1940>
- BELLO, A. A. – JIMOH, A. A. (2018): Some Physical and Mechanical Properties of African Birch (*Anogeissus Leiocarpus*) Timber. *Journal of Applied Sciences and Environmental Management* 22 (1) 79–84. <https://doi.org/10.4314/jasem.v22i1.14>
- CHOWDHURY, M. Q. – ISHIGURI, F. – IZUKA, K. – HIRAIWA, T. – MATSUMOTO, K. – TAKASHIMA, Y. – YOKOTA, S. – YOSHIZAWA, N. (2009): Wood property variation in *Acacia Auriculiformis* growing in Bangladesh. *Wood and Fiber Science* 41 (4): 1–7.
- CHOWDHURY, M. Q. – KHAN, R. – MEHEDI, A. (2013): Wood density variation in four plantation species growing in Bangladesh. *Journal of the Indian Academy of Wood Science* 1–9. <https://doi.org/10.1007/s13196-013-0090-y>
- CHOWDHURY, M. Q. – ISHIGURI, F. – HIRAIWA, T. – TAKASHIMA, Y. – IZUKA, K. – YOKOTA, S. – YOSHIZAWA, N. (2013): Anatomical property variation in *Acacia auriculiformis* growing in Bangladesh. *International Wood Products Journal* 4 (2): 75–80. <https://doi.org/10.1179/2042645313Y.0000000032>
- DAFAALLA, M. E. A. (1998): Variation in the mechanical properties of sunt wood (*Acacia nilotica*.) from different sites growing in Blue Nile Sudan. Master of Science Thesis, University of Khartoum.
- DESCH, H. E. – DINWOODIE, J. M. (1996): Timber, structure, properties, conversion, and use. 7th edition. Macmillan Press Ltd. London.
- EL AMIN, H. M. (1990): Tree and shrubs of the Sudan. Ethecca Press Exeter, United Kingdom.
- FERNANDES, C. – GASPAR, M. J. – PIRES, J. – SILVA, M. E. – CARVALHO, A. – BRITO, J. L. – LOUSADA, J. L. (2017): Within and between-tree variation of wood density components in *Pinus sylvestris* at five sites in Portugal. *European Journal of Wood and Wood Products* 75: 511–526. <https://doi.org/10.1007/s00107-016-1130-2>
- GOLDSMITH, B. – CARTER, D. T. (1981): The Indigenous Timbers of Zambabwe. *Zambabwe Forestry Commission and Research Bulletin* 9: 1–406.
- ISO 3131 (1975): “Wood - Test methods. Determination of density for physical and mechanical tests”, International Organization for Standardization, Geneva, Switzerland.
- ISO 3341 (1975): “Wood - Test methods. Determination of modulus of elasticity in static bending”, International Organization for Standardization, Geneva, Switzerland.
- ISO 3787 (1976): “Wood - Test methods. Determination of ultimate stress in compression parallel to grain”, International Organization for Standardization, Geneva, Switzerland.
- IZEKOR, D. N. – FUWAPE, J. A. – OLUYEGE, A. O. (2010): Effects of density on variations in the mechanical properties of plantation grown *Tectona grandis* wood. *Archives of Applied Science Research* 2 (6): 113–120.
- JAYEOLA, A. A. – AWORINDE, D. O. – FOLORUNSO, A. E. (2009): Use of Wood Characters in the Identification of Selected Timber Species in Nigeria. *Notulae Botanicae Horti Agrobotanici Cluj-Napoc* 37 (2): 28–32.
- KANAPIC, S. – LOUZAPA, J. – LEAL, S. – PEREIRA, H. (2008): within tree and between tree variations of wood density component in cork oak tree in tow site in Portugal. *Forestry* 81 (4): 466–473. <https://doi.org/10.1093/forestry/cpn012>
- KARKI, T. (2001): Variation of wood density and shrinkage in European aspen (*Populus tremula*). *Holz als Roh- und Werkstoff* 59: 79–84. <https://doi.org/10.1007/s001070050479>
- KIAEI, M. – BAKHSHI, R. – SAFFARI, M. – GOLKARI, S. (2015): The within-tree variation in wood density and mechanical properties and their relationship in *Juniperus polycarpus*. *Forest and Environmental Science* 31 (4): 267–271. <https://doi.org/10.7747/JFES.2015.31.4.267>
- KIAEI, M. – FARSI, M. (2016): Vertical variation of density, flexural strength and stiffness of Persian silk wood. *Madera y Bosques* 22 (1): 169–175.

- KOCH, P. (1985): Utilization of hardwoods growing on southern pine sites. U. S. Department of Agriculture and Forest Serv. Library of Congress. Washington.
- MACHADO, J. S. – LOUZADA, J. L. – SANTOS, A. J. A. – NUNES, L. – ANJOS, O. – RODRIGUES, J. – SIMES, R. M. S. – PEREIRA, H. (2014): Variation of wood density and mechanical properties of Black wood (*Acacia melanoxylon* R. Br.). *Materials and Design* 56: 975–980. <https://doi.org/10.1016/j.matdes.2013.12.016>
- MAHGOUB, A. M. (2001): Variation in wood density & shrinkage of twelve species from Kordofan State. Master of Science Thesis, University of Khartoum.
- MAJUMDAR, M. S. M. – DAS, A. K. – SHAMS, M. I. – CHOWDHURY, M. Q. (2014): Effect of age and height position on physical and mechanical properties of rubberwood (*Hevea Brasiliensis*) of Bangladesh. *Bangladesh Journal of Scientific and Industrial Research* 49 (2): 79–84. <https://doi.org/10.3329/bjsir.v49i2.22000>
- MISSANJO, E. – MATSUMURA, J. (2016): Wood Density and Mechanical Properties of *Pinus kesiya* Royle ex Gordon in Malawi. *Forests* 7 (135): 1–10. <https://doi.org/10.3390/f7070135>.
- Mmolotsi, R. M. – Chisupo, O. – Mojeremane, W. – Rampart, M. – Kopong, I. – Monekwe, D. (2013): Dimensional Relations and Physical Properties of Wood of *Acacia saligna*, an Invasive Tree species growing in Botswana. *Research Journal of Agriculture and Forestry Sciences* 1 (6): 12–15.
- Mohammed, A. M. (1999): *The effect of extractives of some Sudanese tree species on portland cement setting*. Master of Science Thesis, University of Khartoum.
- NASROUN, T. H. (2005): Properties and technology of wood, (Arabic Edition). Reyad, Kingdom.
- OGUNWUSI, A. A. – ONWUALU, A. P. – OGUNSANWO, O. Y. (2013): Comparative analysis of wood properties of *Azelia africana* and *Anogeissus leiocarpus* growing in Nigeria. *Chemistry and Materials Research* 3 (3): 1–13.
- PANSHIN, A. J. – DE ZEEUW, C. (1980): Textbook of wood technology. 4th edition. McGraw-Hill Book Company. USA. New York.
- SADIKU, N. A. (2018): Weight, porosity, and dimensional movement classification of some Nigerian timbers. *Journal of Research in Forestry, Wildlife & Environment* 10 (1): 1–10.
- SAHNI, K. C. (1968): Important trees of the Northern Sudan. UNDP and FAO. Khartoum University Press. Khartoum. Sudan.
- SAS (1990): SAS/STAT Guide for personal computer, version 6th edition. SAS Institute Inc. Cary, NC., USA.
- SHMULSKY, R. – JONES, P. D. (2011): Forest Products and Wood science: An Introduction. 6th edition. John Wiley & Sons Inc.
- STEFFENREMA, A. – SARANP, P. – LUNDQVIST, S. – SKRØPPAA, T. (2007): Variation in wood properties among five full-sib families of Norway spruce (*Picea abies*). *Annals of Forest Science* 64: 799–806. <https://doi.org/10.1051/forest:2007062>
- TUMENJARGAL, B. – ISHIGURI, F. – AISO, H. – YUSUKE TAKAHASHI, Y. – NEZU, I. – TAKASHIMA, Y. – BAASAN, B. – CHULTEM, G. – OHSHIMA, J. – YOKOTA, S. (2020): Physical and mechanical properties of wood and their geographic variations in *Larix sibirica* trees naturally grown in Mongolia. *Scientific Reports* 1–14. <https://doi.org/10.1038/s41598-020-69781-7>
- VOGT, K. (1995): Common Trees and Shrubs of Dryland Sudan. SOS Sahel International (UK) ISBN No: 369.
- WESSELS, C. B. – CRAFFORD, P. L. – DU TOIT, B. – GRAHN, T. – JOHANSSON, M. – LUNDQVIST, S. O. – SALL, H. – SEIFERT, T. (2016): Variation in physical and mechanical properties of three drought tolerant Eucalyptus species grown on the dry west coast of Southern Africa. *European Journal of Wood and Wood Products* 74: 563–575. <https://doi.org/10.1007/s00107-016-1016-3>
- XIE, J. – QI, J. – HU, T. – XIAO, H. – CHEN, Y. – HOOP, C. F. D. – HUANG, X. (2017): Anatomical characteristics and physical–mechanical properties of *Neosinocalamus affinis* from Southwest China. *European Journal of Wood and Wood Products* 75: 659–662. <https://doi.org/10.1007/s00107-016-1133-z>
- ZEIDLER, Z. (2012): Variation of wood density in Turkish hazel (*Corylus colurna* L.) grown in the Czech Republic. *Journal of Forest Science* 58 (4): 145–151.

